

### **Comparative Study of Calculated and Actual Dimensions in Shaped Weft-Knitwear**

Journal:	<i>International Journal of Fashion Design, Technology and Education</i>
Manuscript ID	TFDT-2018-0080.R2
Manuscript Type:	Technical Paper
Keywords:	weft knitwear, fully-fashioned, fit, comfort, Armhole shaping

SCHOLARONE™  
Manuscripts

## Comparative Study of Calculated and Actual Dimensions in Shaped Weft-Knitwear

### Abstract

This research explores and quantifies the relationship between traditional mathematical theories used for the calculation of fully-fashioned, weft-knitwear and the physical measurements of knitted garments in order to improve sizing accuracy within knitted garment production. Experiments were conducted to compare and contrast fashioning frequencies for 10-gauge knitted structures, which determined the resultant selvedge dimensions specifically within the armhole region. The trials used the geometrical principle of Pythagoras Theorem to calculate sleeve head and armhole shapes from the stitch densities. The findings identified that the greater distance between the fashionings, the less distortion occurred within the knitted structure and therefore a stronger relationship existed between the calculated seam dimensions and those measured from the physical knitted panels. The research developed new methods for calculating fit and alignment in commercial, fully-fashioned, weft-knitwear. Which provides a more sustainable fully-fashioned knitted product and has the potential to reduce returns, due to size inaccuracies.

**Keywords:** weft-knitwear; fully-fashioned; fit; comfort; armhole shaping

### Introduction

Within traditional commercial knitwear, there are essentially two methods of knitwear production: cut and sew and fully-fashioned. Cut and sew manufacture combines different shapes after the knitted fabric has been cut from individual pattern pieces and sewn together. In contrast, fully-fashioned knitwear manufacture is where the shape of the panel is constructed during the knitting process, by decreasing or increasing the amount of stitches (or wales) within

1  
2  
3 the panel. The resultant garment components (front, back and sleeve panel) are joined together  
4 post-knitting (Brackenbury, 1992). In the last two decades, there has been significant growth  
5  
6 in the sale and production of fully-fashioned, weft-knitted garments (Power, 2008a; Weinswig,  
7  
8 2015). This is due to several factors, including the advancement in flatbed knitting technology  
9  
10 and the ability to combine advanced structures and patterning with complex shaping. The  
11  
12 development of variable stroke within flatbed knitting technology transformed fully-fashioned  
13  
14 knitwear from a product largely associated with the luxury goods market to the preferred  
15  
16 technology for high street fashion knitwear (Brackenbury, 1992; Power, 2007).  
17  
18  
19  
20  
21  
22  
23

24 Flatbed weft-knitting technology has advanced significantly over the last three decades leading  
25  
26 to developments that support the production of fully shaped panels, integral shaped panels and  
27  
28 complete garment production (Black, 2002; Hunter, 2004; Anderson, 2005; Power 2007). The  
29  
30 technology has continued to thrive beyond the millennium with further innovations, including  
31  
32 new takedown mechanisms, yarn feeds, tension control mechanisms and more sophisticated  
33  
34 programming software (Demerol & Dias, 2000; Power, 2017). Design and technical teams have  
35  
36 embraced this revolution across all sectors resulting in advances in performance and functional  
37  
38 wear (for instance, Adidas and Nike took weft knitting into mainstream footwear; Speedo  
39  
40 streamlined swimsuits with compression panels and Armadillo took knitwear into space). This  
41  
42 has produced some complex and innovative designs which have lead to an unprecedented  
43  
44 growth in knitwear within all apparel market segments (Power, 2017). Further to this, the  
45  
46 concept of casual dress has become acceptable in the workplace, with individuals preferring  
47  
48 the comfort and fit of knitted garments offered by improved design and manufacture (Power,  
49  
50 2008b; Memon, 2011; Karl, 2013). This is echoed in trends such as Athleisure, where clothing  
51  
52 such as knitted items usually worn in athletic activities, are worn in the workplace (Goodrum,  
53  
54 2016; Iredale, 2017). The advancement in knitwear technology has led to a surge of creativity  
55  
56  
57  
58  
59  
60

1  
2  
3 and research, as design, technical and marketing teams exploit the boundaries the machinery  
4 offers for improved shape and fit.  
5  
6  
7  
8  
9

10 The focus of this paper is to devise principles to guide the development of 10-gauge fully-  
11 fashioned knitwear production to promote better size, shape and fit in the armhole area. This  
12 was achieved through the following objectives:  
13  
14  
15

- 16 • To quantify the relationship between traditional mathematical theories used for the  
17 calculation of fully-fashioned, weft-knitwear and the actual physical measurements of  
18 the garment.  
19
- 20 • To investigate the alignment of the armhole and sleeve panels in fully-fashioned, weft-  
21 knitwear.  
22
- 23 • Develop and test a new set of principles for calculating 10-gauge fully-fashioned  
24 armholes.  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37

### 38 **Literature Review**

39  
40 Research has shown that greater consumer satisfaction comes from selling superior fitted  
41 garments (Ashdown, 2007; Bodylabs, 2016; Dove, 2017). With the growing crisis in global  
42 garment waste, it is important to reduce the number of returned goods resulting from poor  
43 manufacturing (Allwood, 2006; Fletcher, 2007). The study of body dimensions and sizing for  
44 fashion retail markets is therefore of significant importance (Ashdown, 2007; Power, 2008b).  
45 There has been considerable, recent research into anthropometrics for the clothing industry  
46 (Gupta, 2014), with most studies based on the 1939-40, US Department of Agriculture size  
47 study. More recent studies such as, SIZE – UK, USA, Korea, China, Spain, Mexico, Canada,  
48 Thailand, France and Taiwan and the 2018 INDIAsize, use modern 3D body scanning to obtain  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 measurements (Apeagyei, 2010; Kaushiki, 2018). However, data obtained from any sizing  
4 survey is only of practical use to the fashion industry when it informs the development of size  
5 charts and specifications for garment production. The literature review identified a knowledge  
6 gap in this area, which is specific to knitted garments. One of the challenges associated with  
7 knitwear is that it is possible to produce many different structures within a broad spectrum of  
8 mechanical properties (Mills, 1969; Spencer, 2001; Power, 2008). These structures range from  
9 those with superior drape that skims the body's contours to those, which are structurally rigid  
10 or exhibit elastic properties to hug and support the figure. The properties of the knitted  
11 structures influence the dimensions of garments significantly and their overall conformity to  
12 the body (Eckert et al, 2000).  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28

29 Knitted garment size charts are specific to individual manufacturers as they are associated with  
30 brand differentiation (Aldrich, 2004; Power & Otieno, 2007; Power, 2008b; Brownbridge &  
31 Power, 2010). These are often based on empirical knowledge, gathered over many years,  
32 derived from extensive market knowledge and are ultimately aimed at meeting customer  
33 expectations in regards to size and fit. In the process of producing fully-fashioned knitwear,  
34 the formation of shape is integrated into the manufacturing of the fabric. Hence, the shaped  
35 panels (two sleeves, front panel and back panel), are joined together post-knitting and conform  
36 to the correct dimensions after the garment has been finished (in most cases this involves  
37 scouring and steam pressing to shape garment). It is also dependent on the component fibres  
38 and laundry instructions given to the consumer. If the garment panels are sized incorrectly it  
39 leads to poor fit and high returns of garments to the retailer (Le Pechoux & Ghosh, 2002; Power  
40 and Otieno, 2007, Power, 2008b).  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 In fully-fashioned, weft-knitwear, the shape specification is achieved by calculating the number  
4 of wales (stitches) and courses (rows) and uses a set of mathematical principles combined with  
5 an understanding of knitted structures and resultant fabric properties (Spencer, 2001). The  
6 knitting specification provides information relating to the timing (frequency) of the narrowings  
7 and widenings to achieve the desired shape (as defined by Spencer, 2001). The focus of this  
8 research is prominently in the armhole region of the garment. Diagram 1 illustrates the  
9 difference between a cut and sew style of sleeve and that of a shaped sleeve for both the body  
10 and sleeve panels. In fully-fashioned knitwear, the resultant panel shapes are always a  
11 compromise due to the physical movement of stitches (unlike a cut shape where a proportion  
12 of a stitch may be achieved, fully-fashioned knitwear retains all stitches through relocating  
13 them). Therefore, the actual fit of the sleeve in the 3-D form is a result of the shape of the body  
14 and sleeve panel when joined. This is a complex relationship due to the flexibility of the knitted  
15 structures, the compromise of the knitted panel shaping and the joining of the panel being  
16 completed in the unfinished state. The literature review revealed limited research that has  
17 examined the relationship between final measurements and mathematical theories used for the  
18 calculation of fully-fashioned, weft-knitwear. There is a need to establish a set of guiding  
19 principles and methods for calculating fully fashioned knitwear to promote better size and fit  
20 across the commercial sector and reduce the amount of prototyping required. This set of  
21 principles would improve the sustainability and efficiency of knitting production, resulting in  
22 less garment wastage due to fewer customer returns.

23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51 The armhole is a challenging area in terms of shape and conformity with the human form  
52 (Eckert et al, 2000). The complexity is 4-fold; firstly the translation of the irregular 3D eclipse  
53 shape required for the armhole within the body panels and sleeve head, when flattened into a  
54 2D pattern, is intricate. Diagram 1 illustrates half a traditionally cut armhole shape (cut and  
55  
56  
57  
58  
59  
60

1  
2  
3 sew), compared with that of a knitted fully-fashioned panel. Secondly, in fully-fashioned  
4  
5 knitwear, the formed loops have been moved, which results in the deformation of the structure  
6  
7 (this can be advantageous for comfort, but needs to be accounted for in the knitted  
8  
9 specification). Thirdly, although the stitch densities in the body and sleeve fabric may appear  
10  
11 identical, however they are different due to the natural deformation of the knitted stitch in  
12  
13 panels of different sizes (this is outside the scope of this study). Finally, the armhole area joins  
14  
15 the courses to wales within the selvedge. In the finished state (state of consolidation – which is  
16  
17 defined as the fully relaxed state after scouring, drying in a conditioned environment, steaming  
18  
19 and conditioning for 24 hours) this should represent the same mathematical measurements.  
20  
21 However, in the unfinished state, the knitted dimensions are vastly different, during the  
22  
23 manufacture process. This difference is accounted for by the skilled construction specialist  
24  
25 (known as the linker), who would understand the requirements to achieve a smoothly joined  
26  
27 post-finished seam through their own empirical knowledge.  
28  
29  
30  
31  
32  
33  
34  
35  
36

37 [Diagram 1 near here]  
38  
39  
40  
41  
42

43 It is thus reasonable to conclude that in fully-fashioned weft-knitwear, garment fit and shape  
44  
45 are determined by the knitted structural properties. This makes a single set of knitting  
46  
47 specification recommendations impossible (Brackenbury, 1992; Spencer, 2001; Power, 2008).  
48  
49 It should be acknowledged, that since the calculation of knitted shaped panels is based on a set  
50  
51 of established mathematical principles, these could be used to guide the development of  
52  
53 accurately produced garments for a range of common armhole shapes. This research uses a  
54  
55 plain knitted structure, to develop such a set of guiding principles on a 10-gauge flatbed weft-  
56  
57 knitting machine.  
58  
59  
60

## Materials and Methodology

The research adopted a mixed methods approach that collected, integrated and analysed both quantitative and qualitative data (Corbin & Strauss, 2008; Neuman, 2002). This merger of methods was deemed, appropriate as it established a more cohesive understanding of the research problem by combining mathematical theory with the practical activities of constructing fully-fashioned weft-knitwear. The quantitative approach included experimental research. This is a systematic and scientific approach in which variables are manipulated and the researcher measures and controls change in other variables (Saunders, et al., 2016). In this study, it included a series of experiments devised to measure the calculation of fully-fashioned knitwear and the physical measurements of the garment within the armhole area. These identified new relationships between the dimensions of knitted garment armholes and guiding principles to improve alignment, fit and comfort during wear. A qualitative approach utilising practice-based research supported the quantitative experiments. This practice utilized commercial standard knitwear technology to create garment samples. Various experiments were conducted on the samples to determine the impact on the selvedge dimensions. The samples were scrutinized, to consider how alignment, fit and comfort improved when the knitted garments were worn on the human body.

The geometry principle of Pythagoras Theorem, was selected as a theoretical formula to calculate the correct selvedge dimensions for knitted armhole measurements (Posamentier, 2010; Maor, 2007). This is a commonly understood geometrical principle which is used across the knitwear sector to calculate the correct armhole size from two standard given measurements (the chest and across the shoulders). In knitwear design, the desired armhole shape is usually elliptical however in fully-fashioned weft-knitwear the curved shape of a cut armhole, is



1  
2  
3 impossible to achieve due to the fashioning (narrowing) of stitches. Theoretically, it is possible  
4  
5 to narrow by 1,2,3,4 stitches at a time. In practice narrowing beyond 2 stitches, in a single  
6  
7 narrowing action results in a bulking of the fabric or at worst, production issues (including yarn  
8  
9 bursts) due to excessive pressure applied during the re-location of the stitches (Spencer, 2001).  
10  
11 In commercially produced knitwear, it is accepted practice to narrow by a maximum of 2  
12  
13 stitches (or 1 if there are sufficient courses to accommodate this). Pythagoras Theorem is useful  
14  
15 to ensure there are sufficient courses available to execute the desired reduction in width. A  
16  
17 right-angled, triangle, can be used as overlay to enable the programmer or technician to  
18  
19 calculate the number and frequency of reductions in the knitted stitches required in order to  
20  
21 achieve the correct armhole dimensions (Diagram 2).  
22  
23  
24  
25  
26  
27  
28  
29

30 [Diagram 2 near here]  
31  
32  
33

34 A series of five experiments were conducted (Table 1) on a 10-gauge Stoll, CMS knitting  
35  
36 machine (this is a popular gauge in mainstream knitwear - Power, 2008a). Technical parameters  
37  
38 were controlled, by balancing the knitting cams in both knitting directions to deliver the stitch  
39  
40 length as detailed in Table 1. The machine was calibrated at the start of each day by adjusting  
41  
42 the tensions to deliver consistent stitch lengths, prior to loading a new knitting instruction  
43  
44 programme. This was repeated at any yarn changes. Three different yarns were used in the  
45  
46 experiments, all of which were commercially available. It is commonly accepted that dark  
47  
48 colours can change the yarn properties and resultant stitch densities, even when knitted at the  
49  
50 same stitch length, therefore the selected yarns were of a light colour as near to ecru as possible  
51  
52 to avoid any influence of over dye. Initially 2/28 high bulk acrylic was used to establish a set  
53  
54 of common principles due to low cost and availability. Later the yarn was changed to 2/30  
55  
56  
57  
58  
59  
60

1  
2  
3 Cashwool (a blend of wool and cashmere), which is a more expensive yarn associated with  
4  
5 higher quality garment production.  
6  
7

8  
9 The final experiment used a slightly heavier yarn which was aligned to garment production and  
10  
11 fashion trends at the time of the research. To minimise the effect of the yarn changes, the stitch  
12  
13 lengths were adjusted and stitch densities were re-calculated to ensure the tightness factor  
14  
15 remained at a constant value (Table 1). The yarn was stored in a controlled condition prior to  
16  
17 delivery in accordance with the method described in BS EN ISO 139 (20 degrees Celsius +/- 2  
18  
19 and 65% Relative Humidity 65% +/- 4). The takedown speed, was regulated throughout the  
20  
21 trials. Since the trials were completed on similar dimensions of fabric, this was deemed to have  
22  
23 a negligible effect on resultant stitch density. The stitch densities detailed in Table 1, are in the  
24  
25 state of consolidation (light scour by hand), short spin and air dried flat (in the controlled  
26  
27 environment defined above). The resultant tightness factors for all fabrics was 1.52. Munden  
28  
29 (1962) associated a cover factor of 1.25 with high quality knitted fabrics (by simple conversion  
30  
31 the resulted tightness factor for high quality fabric is 1.47). In-order to assess fit and comfort  
32  
33 during wear, the reduction in dimensions between the chest and the shoulder was 14cm  
34  
35 (experiments 1 – 4, this is a common reduction used for a basic notch shape - Power, 2008b).  
36  
37 In experiment 5, the dimensions between the chest and shoulders were adjusted to 10cm to  
38  
39 reflect a closer fitting to the body, thus accommodating a more fitted armhole and sleeve width  
40  
41 (inset sleeve). The two-needle narrowing as detailed in Diagram 1, used a six-needle movement  
42  
43 from the selvedge (reducing the width by two needles) to ensure a smooth selvedge area for  
44  
45 make-up. This is an acceptable and standard commercial practice (Diagram 1). The basic  
46  
47 relationship of Pythagoras Theorem is illustrated in Diagram 3.  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

[Table 1 near here]

1  
2  
3 [Diagram 3 near here]  
4  
5  
6  
7  
8

## 9 **Results**

10  
11  
12 The main objective of experiment 1 was to examine the relationship between theoretical  
13 dimensions and those yielded in the knitted fabrics state of consolidation, to determine the  
14 underpinning framework for the study. The number of wales and courses in the sample  
15 remained constant throughout the experimentation. Eighteen fashionings (narrowings) were  
16 used to reduce the width of the fabric by 7cm at each selvedge (thus, representing the chest to  
17 shoulder decrease for one armhole), over intervals of 1, 2, 3 and 4 courses (fashioning  
18 frequency). The calculated 'dimension b' (Diagram 3) remained constant at 7cm and the  
19 calculated 'dimension a' was increased due to the change in the fashioning frequency. The  
20 theoretical measurements are displayed in Table 2, along with the off-machine dimensions and  
21 the physical knitting dimensions in the state of consolidation. The state of consolidation is  
22 defined as a light scour (by hand) using a standard detergent solution (BS EN ISO 6330, 2012  
23 – reference 1) in a tepid water (between 30-35 degrees Celsius). There was a short spin, and  
24 the fabric was dried flat followed with a 5 second burst of steam, then finally stored flat for 24  
25 hours in a controlled environment as defined for the yarn conditioning (BS EN ISO139, 2005).  
26 It should be noted that this is a controlled experiment and it would be extremely rare to use a  
27 fashioning frequency of one course between fashionings in a commercial setting, due to the  
28 distortion that is created in the finished fabric or the stress put on the yarn resulting in  
29 dropped/burst stitches.  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55

56 The distortion is evident from the results displayed in Table 2. The shaded column (dimension  
57 c) illustrates the knitted selvedge to be 54% of the calculated dimension. A difference of 46%  
58  
59  
60

1  
2  
3 is evident in the knitted sample for the lowest fashioning frequency (dimension c), whilst a  
4 negligible 2% is calculated at the higher frequency of four courses. Conclusively, from this  
5  
6  
7  
8 basic experiment, the greater the fashioning frequencies are apart, the closer the dimensions in  
9  
10 the knitted sample are to those calculated using Pythagoras Theorem. The issue of selvedge  
11  
12 distortion within fully-fashioned knitwear has been highlighted in prior research (Mills, 1967),  
13  
14 where trigonometry was used to access the differences in angles produced by different  
15  
16 fashioning frequencies. The outcome was a series of adjustments to basic trigonometry  
17  
18 functions to account for the distortion to the dimensions, due to the knitting construction  
19  
20 process. Three fashioning frequencies were explored in Mills (1967) work (1, 4 and 10 courses)  
21  
22 and similarities can be drawn from the work presented in this paper to that of Mills earlier  
23  
24 study. Early work in knitting geometry established the reason why the measured knitted stitch  
25  
26 was smaller than the theoretical stitch within weft-knitwear and this was due to the mechanical  
27  
28 action of forming the stitch. The tension required to pull yarn from the package during the  
29  
30 stitch cams increases rapidly and it becomes easier to rob yarn from the previously formed  
31  
32 stitches rather than yarn from the package (Knapton & Munden, 1966a; Spencer, 2001). Prior  
33  
34 research has discussed robing of yarn for stitch formation in detail (Knapton & Munden, 1966a,  
35  
36 1966b; Peat and Spicer, 1974; Pusch et al., 2000; Spencer, 2006), however since Mills 1967  
37  
38 study, there has been no specific research related to distortions in knitting selvedge where  
39  
40 movement of stitches occur. This research substantiates Mills work, using an alternate method  
41  
42 (more aligned to commercial production). It would be reasonable to conclude from this  
43  
44 research and Mills study, that it would be almost impossible to achieve a correlation of 100%  
45  
46 in shaped weft-knitwear and therefore a tolerance band should be acceptable. It can also be  
47  
48 concluded that as fashioning frequencies increase beyond four courses, the physical  
49  
50 measurements would remain constant at 98% of the theoretical measurement, and increases in  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 fashioning frequencies (more courses between the narrowing actions) result in less selvedge  
4  
5 distortion.  
6  
7  
8  
9

10 [Table 2 near here]  
11  
12  
13

14 Experiment 2 expanded the preliminary investigation (experiment 1) from single panels to  
15 multiple (body and sleeve components) to assess the relationships between the theoretical and  
16 physical dimensions in garment form. It compared two commercially acceptable empirical  
17 methods (notch and raglan) designed to align the sleeve and body panels (Diagram 4). For the  
18 purpose of the research, the *notch* is defined as the armhole shape, which has a geometry that  
19 aligns mathematically. Diagram 4 provides a schematic figure to illustrate the relationship of  
20 the aligning components, whereby dimensions X on the body and sleeve panel are equal lengths  
21 in centimetres and the dimensions of Y, are also equal in centimetres. Thus, the two triangles  
22 on the separate garment components (sleeve and body) should form hypotenuses of identical  
23 dimensions and fit together theoretically. In contrast the research defines the *raglan* method  
24 (not to be confused with the raglan style sleeve) as the dimensions of Y being equal in courses  
25 (knitted rows) on each of the sleeve and body components; X being equal in centimetres (on  
26 both garment components) and the dimension of Z (body component) being the calculated  
27 reduction required between the chest and the shoulder measurements (7cm). The difference  
28 between the two methods is that the hypotenuse of the *notch* should align post-finishing and  
29 the hypotenuse of the *raglan* should align pre-finishing. In knitwear there is always a  
30 compromise since the courses and wales shrink in different proportions during finishing  
31 (usually the length reduction is greater than the width). The fully-fashioned body and sleeve  
32 components were joined pre-finishing, thus, the seams were not equal to the intended calculated  
33 dimensions in the finished state. This is clearly demonstrated in the differences between pre-  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 finishing dimensions (*off machine*) and post-finishing (*physical knitted*) in Table 3. Only the  
4 selvedge of the component panels (sleeve and body) are joined, resulting in a single dimension  
5 for the hypotenuse (dimension  $c$ ). This is the paradox of shaped knitwear, which has relied on  
6 the empirical knowledge of the technician to judge the best fitting calculation method.  
7  
8  
9  
10  
11  
12  
13  
14

15 A fully-fashioned sleeve and body panel were knitted, to examine the alignment of the two  
16 body and sleeve components. The two methods were studied over three different body  
17 fashioning frequencies (2, 3 and 4 courses). The sleeve fashioning frequencies were calculated  
18 mathematically (using Pythagoras Theorem) to ensure the components aligned as described in  
19 Diagram 4. Table 3 illustrates the theoretical dimensions compared to the physical knitted  
20 panels. The experiment set a crude line between the two empirical methods used to align the  
21 sleeve and the body panel. The shaded column (percentage difference-*dimension c*)  
22 demonstrates that if the number of fashionings on the sleeve is less than the body, the *notch*  
23 method should be used. If the body and sleeves are equal in the number of fashionings, either  
24 method could be used. However, if the sleeve consists of more fashionings than the body, the  
25 optimum method to use is that of the *raglan*.  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

45 [Diagram 4 near here]

46  
47 [Table 3 near here]

48  
49  
50  
51  
52  
53  
54 After the initial experiment, two higher fashion frequencies were explored (6 and 8 courses),  
55 the raglan method was compared with a new method, which reduced the number of courses by  
56 10% within the sleeve head area. The shaded columns (percentage difference) in Table 4  
57  
58  
59  
60

1  
2  
3 illustrate the theoretical dimensions compared to the actual knitted samples in the state of  
4 consolidation (post-finishing). The results demonstrate a good alignment between the selvedge  
5 measurements in the knitted sample and those calculated (between 93% and 108% for  
6 dimension C using the raglan method). The 10% reduction in courses (in sleeve head) however,  
7  
8 appears to result in a slightly better alignment between the theoretical dimensions and the  
9  
10 physical (99-106%). The results of experiment 3 expand the findings from experiments 1 and  
11  
12 2. Thus, there is evidence to suggest that increasing fashioning frequencies above 4 courses in  
13  
14 the body results in knitting dimensions within 10% of the theoretical dimensions. This set of  
15  
16 garments were examined further, to determine their fit to the human form. This identified that  
17  
18 when worn, there was a noticeable distortion in the shoulder area of the garment. This was due  
19  
20 to the steepness of the angle in which the sleeve fell, as a direct result of the increase in the  
21  
22 sleeve head area (Diagram 5). Conclusively, the experiment was useful in terms of assessing  
23  
24 the theoretical relationships between the calculated methods and actual knitting dimensions.  
25  
26 However, there needed to be further modifications to the shape of the body and sleeve panels  
27  
28 if the resultant garment was going to conform to the human form. In weft-knitwear, the sleeve  
29  
30 width is usually reduced therefore a sloped angle is achieved in the sleeve and a sloped shoulder  
31  
32 is used to reduce distortion in the shoulder area. This enables a closer knitting silhouette and  
33  
34 fit to be developed, which is explored further in experiments 4 and 5.  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54

[Table 4 near here]

55 Experiment 4 modified one of the dimensions in the sleeve panel (the sleeve width, was reduced  
56  
57 by 2cm). Whilst the research acknowledges the shoulder should be sloped to reflect the actual  
58  
59 shape of the human form, in the experiment it was kept straight. This helped to determine a  
60

1  
2  
3 two-step approach to access any distortion identified in fit trials of the knitted garments that  
4 resulted from changing multiple components simultaneously. The data, is not presented in a  
5 table because the dimensions resulted in a concluding set of results. In all (body) fashioning  
6 frequencies (2, 3, 4, 6, 8) the raglan method of aligning the sleeve panel produced dimensions  
7 closer to the calculated dimension. In the fit trials, the fashioning frequency increased but less  
8 distortion occurred in the shoulder area. In all trials, however distortion in the shoulder area  
9 was evident beyond reasonable considerations for a commercial garment. In any knitted  
10 garment, the shoulder seam should lie flat to the body and flex with arm movement. In the case  
11 of a straight shoulder with a fitted sleeve, an excess of fabric occurred when the arm was raised.  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27

28 [Diagram 5 near here]  
29  
30  
31  
32  
33

34 The final experiment explored a knitted armhole shape that fits more closely to the human form  
35 (inset sleeve – Diagram 5). The general principles learned from the prior experiments were  
36 applied as the sleeve width remained at 29cm (flat). A shoulder slope of 3cm, was introduced  
37 on the body panel and the armhole was calculated using Pythagoras Theorem to equal 21cm.  
38 The 10% reduction on the raglan method was used to align the sleeve and body panels. Five  
39 separate trials were knitted and Table 5 displays the average results, which demonstrate good  
40 conformity (within the 10% tolerance) between the theoretical calculated results and those  
41 produced in the post-finished, knitted garment. When worn on the human form the sleeve  
42 conformed to the body contour and was deemed, comfortable by the wearer in the initial fit  
43 trials. In summary, the inset sleeve creates a sophisticated armhole that conforms to the body.  
44 The preferred method of calculation was the raglan with a 10% reduction in the sleeve head  
45 area. This resulted in an overall armhole shape that fitted the human form comfortably.  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



1  
2  
3 [Table 5 near here]  
4  
5  
6  
7

## 8 **Conclusions**

9  
10 The experiments identified a quantifiable relationship between the theoretical dimensions  
11 calculated using the principle of Pythagoras Theorem and the physical dimensions produced in  
12 the fully-fashioned selvedge (10 gauge weft-knitwear). The following principles were  
13 therefore, observed. A fashioning frequency of 1 course was unacceptable, fashioning  
14 frequencies of 2 and 3 courses resulted in the selvedge of the knitted samples measuring  
15 between 83-86% of the theoretical dimensions. The optimum fashioning frequency for shaping  
16 is 4 courses or above (the knitted selvedge dimensions were found to be 98% of the theoretical  
17 calculated). Further to this a comprehensive set of guiding principles were established. If the  
18 number of fashionings on the sleeve was less than the body, when aligning the body panels the  
19 notch alignment method is appropriate for use. However, if the sleeve and body fashionings  
20 are equal, either method is suitable. Finally, should the sleeve comprise of more fashionings  
21 than the body, the raglan method is appropriate for use. Further experimentation resulted in a  
22 new method for alignment, which reduced the raglan dimension by 10% in the sleeve head  
23 area, creating better conformity between the sleeve and the body panels during make-up and  
24 after finishing. This method was further explored in the use of an inset sleeve (a reduced sleeve  
25 widest, across shoulder and a sloped shoulder). The findings discovered the inset sleeve  
26 creates a sophisticated armhole that conforms to the body and the 10% reduction (raglan  
27 method) was the preferred alignment method to ensure the sleeve head fits into the armhole  
28 shape and conforms to the human body.  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55

56 Ultimately, it is possible to quantify the relationship between traditional mathematical theories  
57 used for the calculation of fully-fashioned weft-knitwear and the actual physical measurements  
58  
59  
60

1  
2  
3 of the garment. Although these trials focussed on calculating sleeve head and armhole shapes  
4  
5 from the stitch density of 10-gauge knitwear, it can be recommended that the set of guiding  
6  
7 principles could be used to improve the alignment of seam dimensions on all knitted panels of  
8  
9 fully-fashioned weft-knitting obtained from similar gauges (8 and 12 gauges). Further  
10  
11 experimentation would be required to extend these principles for chunky (2.5 – 7 gauges) and  
12  
13 ultra-fine knitwear (14 – 21 gauges) due to the dramatic difference in structural properties, yarn  
14  
15 types and resultant tightness factor of the fabrics. The adoption of these guiding principles in  
16  
17 knitwear manufacture for garments produced on a 10-gauge machine (with similar yarn counts  
18  
19 and stitch lengths) will result in better alignment of the sleeve components during manufacture,  
20  
21 and improved fit/comfort (potentially improve consumer satisfaction and increasing sales and  
22  
23 reducing returns). The results also significantly expand the depth of research in global knitwear  
24  
25 technology and its application to the finished product. Future research can explore how  
26  
27 improved fit will continue to maintain consumer satisfaction as well as encouraging designers  
28  
29 to incorporate more innovative knitwear shaping within their collections.  
30  
31  
32  
33  
34  
35  
36  
37

### 38 **References**

- 39  
40 Anderson, C. (2005). Pringle: The Renaissance of a Brand. *Knitting International*, 112(1323),  
41  
42 24-26.  
43  
44 Aldrich, W. (2004). *Metric Pattern Cutting* (4 ed.). UK: Blackwell Publishing.  
45  
46 Allwood, J. M. (2006). *Well Dressed?* Technical Annex. UK: University of Cambridge.  
47  
48 Apegyei, P. (2010). Application of 3D Body Scanning Technology to Human Measurement  
49  
50 for Clothing Fit. *International Journal of Digital Content Technology and its Application*, 4(7),  
51  
52 58-68.  
53  
54  
55 Ashdown, S. (2007). *Sizing in Clothing*. Cambridge: Woodhead.  
56  
57  
58 Black, S. (2002). *Knitwear in Fashion*. UK: Thames and Hudson Ltd.  
59  
60

- 1  
2  
3 Body Labs. (2016, November 13). Retail Fit Survey. Retrieved from  
4  
5 <https://www.slideshare.net/daniellaurence/body-labs-2016-retail-survey-fit>  
6  
7  
8 Brackenbury, T. (1992, November). *Knitted Clothing Technology*. UK: Blackwell Science.  
9  
10 Brownbridge, K., & Power, E. J. (2010). *Anthropometric Practices & the complete Garment*.  
11 *Proceedings of the Textile Institute Centenary Conference*. Manchester, UK. Textile  
12 Institute.  
13  
14  
15 BS EN ISO 139. (2005). *Standard Atmospheres for Conditioning and Testing*. British  
16 Standards: BSI Group.  
17  
18 BS EN ISO 6330. (2012). *Textiles. Domestic Washing and Drying Procedures for Textile*  
19 *Testing*. British Standards: BSI Group.  
20  
21  
22 Corbin, J., & Strauss, A. (2008). *Basics of Qualitative Research*. London: Sage Publications,  
23 Inc.  
24  
25 Demiroz, D., & Dias, T. (2000). A Study of the Graphical Representation of Plain Knitted  
26 Structures. *Journal of the Textile Institute*, 91(4), 463-480.  
27  
28  
29 Dove, T. (2017, July). *Women's Clothing Choices are Being Inhibited by Poor Fit*. *Advances*  
30 *in Physical Ergonomics and Human Factors. Proceedings of the AHFE 2017 International*  
31 *Conference on Physical Ergonomics and Human Factors*. Los Angeles, USA: Springer.  
32  
33  
34  
35  
36  
37 Eckert, C. M., Cross, N., & Johnson, J. H. (2000). Intelligent Support for Communication in  
38 Design Teams: Garment Shape Specifications in the Knitwear Industry. *Design Studies*, 21(1),  
39 99-112.  
40  
41  
42  
43  
44 Fletcher, K. (2008). *Sustainable Fashion and Textiles*. UK: Earthscan.  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 Iredale, A. (2017). *The Athleisure Phenomenon: An Investigation into new Developments in*  
4 *the Fashion Sportswear industry* (Unpublished master's thesis). University of Leeds, UK.  
5  
6  
7  
8 Karl, K. A., Hall, L. M., & Peluchette, J. V. (2013). City Employee Perceptions of the Impact  
9  
10 of Dress and Appearance: You Are What You Wear. *Public Personnel Management*, 42(3),  
11  
12 452-470.  
13  
14  
15 Kaushiki, D. (2018, March 5). An 'India Size Chart': What Does It Mean and Why do we Need  
16  
17 It. Retrieved from [https://timesofindia.indiatimes.com/city/delhi/an-india-size-chart-what-](https://timesofindia.indiatimes.com/city/delhi/an-india-size-chart-what-does-it-mean-and-why-do-we-need-it/articleshow/63157572.cms)  
18 [does-it-mean-and-why-do-we-need-it/articleshow/63157572.cms](https://timesofindia.indiatimes.com/city/delhi/an-india-size-chart-what-does-it-mean-and-why-do-we-need-it/articleshow/63157572.cms)  
19  
20  
21  
22 Knapton, J.J.F., & Munden, D.L. (1966a). A Study of the Mechanism of Loop Formation on  
23  
24 Weft-Knitting Machinery: Part II: The Effect of Yarn Friction on Yam Tensions in Knitting  
25  
26 and Loop Formation. *Textile Research Journal*, 36(12) 1081-1091.  
27  
28  
29 Knapton, J.J.F., & Munden, D.L. (1966b) A Study of the Mechanism of Loop Formation on  
30  
31 Weft-Knitting Machinery: Part I: The Effect of Input Tension and Cam Setting on Loop  
32  
33 Formation. *Textile Research Journal*, 36(12) 1072-1080.  
34  
35  
36 Le Pechoux, B., & Ghosh, T.K. (2002). 'Standard Sizing and Fit Testing Applied to Women's  
37  
38 Hosiery'. *Textile Progress*, 32(1), 1-59.  
39  
40  
41 Maor, E. (2007). *The Pythagorean Theorem: A 4,000-year History*. New Jersey: Princeton  
42  
43 University Press.  
44  
45  
46 Memon N. A. (2011). Knitwear Industry: Playing Vital Role in Value Addition, *Pakistan*  
47 *Textile Journal*, 34-36.  
48  
49  
50 Mills, R. W. (1967). The Shaping of Plain Fabrics. *Journal of the Textile Institute*, 58(1), 40-  
51  
52 46.  
53  
54  
55 Munden, D. L. (1962). Specification of the Construction of Knitted Fabrics. *Journal of the*  
56  
57 *Textile Institute*, 51(1), 628-631.  
58  
59  
60

1  
2  
3 Neuman, L. (2002). *Social Research Methods: Qualitative and Quantitative Methods*. London:  
4  
5 Pearson.

6  
7 Peat, D., and Spicer, E.R. (1974). Yarn Movement and Tension during Loop Formation in  
8  
9 Circular Knitting. *Journal of the Textile Institute*, 65(7), 388-393.

10  
11 Posamentier, A. (2010). *The Pythagorean Theorem: The Story of Its Power and Beauty*. New  
12  
13 York: Prometheus Books.

14  
15 Power, E. J. & Otieno R. (2007, March). *Study of Anthropometrical Data in Knitted Garments*.  
16  
17 *Proceedings of the Textile Institute 85th World Conference*, Colombo, Sri Lanka: Textile  
18  
19 Institute.

20  
21 Power, J. (2007). Functional to Fashionable: Knitwear's Evolution Throughout the Last  
22  
23 Century and Into the Millennium. *Journal of Textile Apparel Technology and Management*,  
24  
25 5(4), 1-16.

26  
27 Power, J. (2008). Developments in Apparel Knitting Technology. In Fairhurst, C (Ed.),  
28  
29 *Fairhurst Advances in Apparel Production*. Cambridge: Woodhead.

30  
31 Power, J. (2008a). Measuring up Knitting International. *World Textile Publications*, 114(1360),  
32  
33 40-41.

34  
35 Power, J. (2008b). Shaping Progress Knitting International. *World Textile Publications*,  
36  
37 114(1358), 34-35.

38  
39 Power, J. (2017). Advanced Knitting Technologies for High Performance Apparel. In J.  
40  
41 McLoughlin & T. Sabir (Eds.), *High-Performance Apparel: Materials, Developments and*  
42  
43 *Applications*. London: Elsevier.

44  
45 Power, E. J., & Oteino, R. (2008, November). *Investigating the Relationship Between*  
46  
47 *Anthropometrical Data and Fully Shaped Knitted Garments in UK Manufacturing*.  
48  
49 *Proceedings of the Textile Institute 86th World Conference*. Hong Kong, China. Textile  
50  
51 Institute.

1  
2  
3 Pusch, T., Wunsch, P., & Offermann, P. (2000). Dynamics of Yam Tension on Knitting  
4 Machines. *AUTEX Research Journal*, 1(2) 54-63.

5  
6  
7  
8 Saunders, M., Lewis, P., & Thornhill, A. (2016). *Research Methods for Business Students*. UK:  
9 Pearson.

10  
11  
12 Spencer, D. (2001). *Knitting Technology*. Cambridge: Woodhead.

13  
14 Spencer, D. (2006). *Knitting Technology 3<sup>rd</sup> Edition*. Cambridge: Woodhead.

15  
16  
17 Weinswig, D. (2015). A Deep Dive into Sweaters. *Fung Business Intelligence Centre*, 1-22.  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

## Tables

No	Purpose of experiment	Yarn	Stitch density	Stitch length	Tightness Factor <u>(TF)</u> *
1	Examine into the relationship between theoretical dimensions and those yielded in the knitted fabrics state of consolidation.	2 x 2/28 Acrylic	7.22 courses/cm 5.13 wales/cm	161cm/200 needles	1.52
2	Comparative study 1 of calculation methods used for an optimum fully fashioned notch armhole.	2 x 2/28 Acrylic	7.22 courses/cm 5.128 wales/cm	161cm/200 needles	1.52
3	Comparative study 2 of calculation methods used for an optimum fully fashioned notch armhole.	2 x 2/30 Cashwool	7.00 courses/cm 5.00 wales/cm	155cm/200 needles	1.52
4	Comparative study 3 of calculation methods used for an optimum fully-fashioned notch armhole with reduced sleeve widest.	2 x 2/30 Cashwool	7.00 courses/cm 5.00 wales/cm	155cm/200 needles	1.52
5	To apply the theories established from Experiment 1-4 to a garment with an inset sleeve.	2x 2/27 Cashwool	6.51 courses/cm 4.70 wales/cm	158cm/200 needles	1.52

$$* TF = \frac{\sqrt{tex}}{\text{stitch length (mm)}}$$

Table 1 – Experiment framework for study

Fashioning frequency	Theoretical dimensions (cm)			Off machine dimensions (cm)			Physical knitted dimensions (state of consolidation) (cm)			% difference theoretical and physical		
	a	b	c	a	b	c	a	b	c	a	b	c
1 course	2.4	7.0	7.4	2.0	4.0	4.4	1.5	4.5	4.0	64	64	54
2 courses	4.7	7.0	8.4	6.0	6.0	7.5	4.7	6.5	7.0	100	93	83
3 courses	7.1	7.0	9.9	6.5	7.3	7.5	7.0	6.5	8.5	99	93	86
4 courses	9.4	7.0	11.7	11.0	7.0	13.0	9.5	6.5	11.5	101	93	98

Table 2 Comparison of fully-fashioned theoretical dimensions and Physical



Calculation method	Garment component	Number of fashionings	Fashioning frequency	Theoretical dimensions (cm)			Off machine dimensions (cm)			Physical knitted dimensions (cm) (state of consolidation)			% difference theoretical and physical		
				a	b	c	a	b	c	a	b	c	a	b	c
Notch	Body	18 x 2 ndl narrowing	2 courses	4.7	7.0	8.4	6.0	6.0	7.5	4.7	6.5	7.0	100	93	
	Sleeve	12 x 2 ndl narrowing	4.5 courses	7.0	4.7	8.4	7.5	4.5	9.0	7.0	4.7		100	100	83
Notch	Body	18 x 2 ndl narrowing	3 courses	7.1	7.0	9.9	6.0	7.0	9.0	6.0	6.5	8.8	85	93	
	Sleeve	18 x 2 ndl narrowing	2.94 courses	7.0	7.1	9.9	7.5	8.0	10.0	7.0	6.0		100	85	89
Notch	Body	18 x 2 ndl narrowing	4 courses	9.4	7.0	11.7	11.0	8.0	13.0	9.0	6.5	10.5	96	93	
	Sleeve	24 x 2 ndl narrowing	2.17 courses	7.0	9.0	11.7	9.0	10.5	16.0	6.5	8.5		93	94	90
Raglan	Body	18 x 2 ndl narrowing	2 courses	4.7	7.0	8.4	6.0	6.0	7.5	4.0	6.5	6.0	85	93	
	Sleeve	12 x 2 ndl narrowing	3 courses	4.7	4.7	6.6	5.0	5.0	6.5	5.0	4.0		106	85	71
Raglan	Body	18 x 2 ndl narrowing	3 courses	7.1	7.0	9.9	6.0	7.0	9.0	6.0	6.5	8.8	85	93	
	Sleeve	18 x 2 ndl narrowing	3 courses	7.1	7.1	10.0	7.5	8.0	10.0	7.0	6.0		99	85	89
Raglan	Body	18 x 2 ndl narrowing	4 courses	9.0	7.0	11.7	11.0	8.0	13.0	9.0	6.5	11.5	100	93	
	Sleeve	24 x 2 ndl narrowing	3 courses	9.0	9.0	12.7	11.5	11.0	15.5	8.0	9.0		88	100	98

(Where the fashioning frequency is a fractional number alternate frequencies have been used – 2.5 courses would equate to 2 courses, 3 courses alternating)

Table 3 – Using two different empirical methods to calculate knitted armhole shapes

Calculation method	Garment component	Number of fashionings	Fashioning frequency	Theoretical dimensions (cm)			Off machine dimensions (cm)			Physical knitted dimensions (state of consolidation) (cm)			% difference theoretical and physical		
				a	b	c	a	b	c	a	b	c	a	b	c
Raglan	Body	18 x 2 ndl narrowing	6 courses	14.6	7.0	16.2	16.5	8.7	18.5	14.0	6.5	15	96	93	93
	Sleeve	36 x 2 ndl narrowing	2.9 courses	14.6	14.6	20.6	16.0	15.0	21.0	16.0	12.5		110	86	
Raglan	Body	18 x 2 ndl narrowing	8 courses	19.1	7.0	20.3	21.2	8.7	23.5	20.0	6.0	22	105	86	108
	Sleeve	48 x 2 ndl narrowing	2.85 courses	19.1	19.1	27.0	20.0	19.7	28.0	20.0	15.5		105	81	
10% Reduction	Body	18 x 2 ndl narrowing	6 courses	14.6	7.0	16.2	16.5	8.7	18.5	13.5	7.0	16	92	100	99
	Sleeve	36 x 2 ndl narrowing	2.6 courses	13.1	14.6	19.2	15.0	15.0	19.0	13.0	12.5		99	86	
10% Reduction	Body	18 x 2 ndl narrowing	8 courses	19.1	7.0	20.3	21.2	8.7	23.5	20.0	7.0	22	105	100	106
	Sleeve	48 x 2 ndl narrowing	2.5 courses	17.1	19.1	25.6	19.0	19.7	27.0	17.5	16.0		102	84	

(Where the fashioning frequency is a fractional number alternate frequencies have been used – 2.5 courses would equate to 2 courses, 3 courses alternating)

Table 4 – Using two different empirical methods to calculate knitted armhole shapes

Dimension	Theoretical (cm)	Physical knitted (cm)	% difference
Length	43	42	97.7
Chest	46	44	95.7
Shoulder	34.5	32	92.8
Armhole	21	21	100.0
Underarm	46	46	100.0
Sleeve widest	14.5	14	96.6
cuff	6	6	100.0

Table 5 – Inset sleeve – body and sleeve dimensions

1  
2  
3 List of Figures  
4

5 Diagram 1 - Traditionally cut armhole shape V fully-fashioned armhole.  
6

7 Diagram 2 - Armhole geometry  
8

9 Diagram 3 - Pythagoras Theorem  
10

11 Diagram 4 - Garment component alignment  
12

13 Diagram 5 – Inset sleeve panel alignment  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

For Peer Review Only

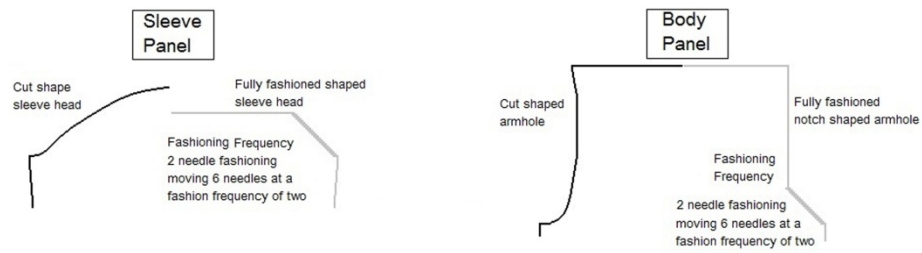


Diagram 1 - Traditionally cut armhole shape V fully-fashioned armhole

135x34mm (600 x 600 DPI)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

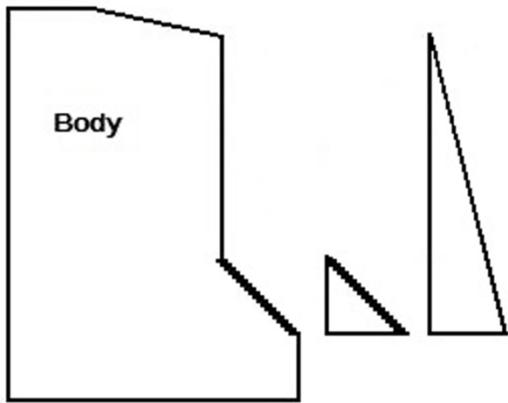


Diagram 2 - Armhole Geometry  
131x69mm (600 x 600 DPI)

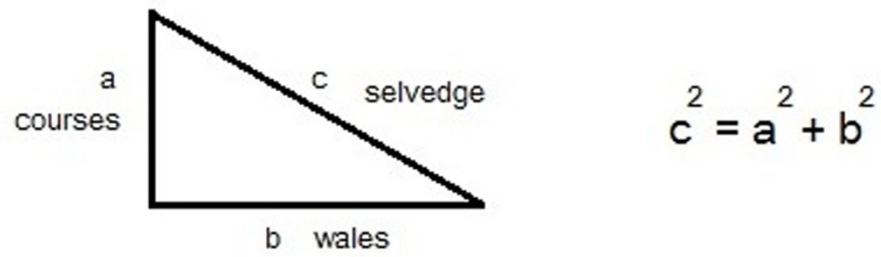


Diagram 3 - Pythagoras Theorem

113x34mm (600 x 600 DPI)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

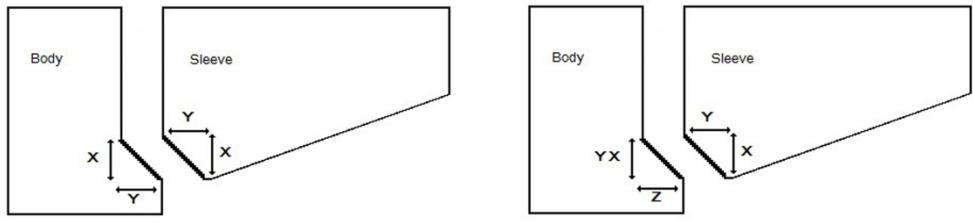


Diagram 4 - Garment component alignment

247x69mm (600 x 600 DPI)



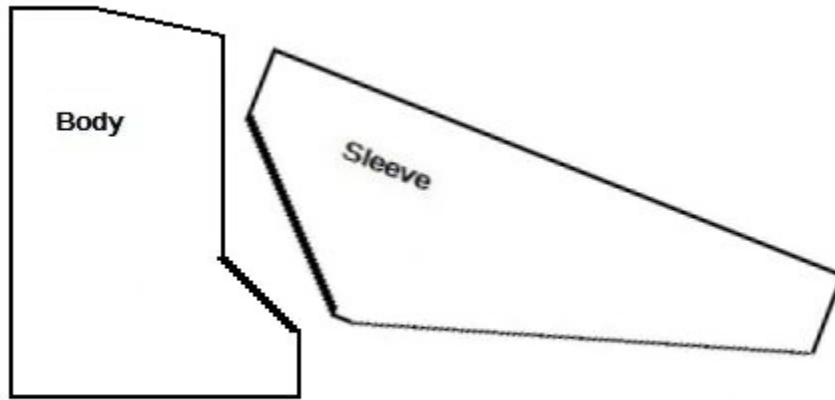


Diagram 5 - Inset sleeve panel alignment

131x69mm (96 x 96 DPI)